arXiv:1303.3396v1 [cond-mat.supr-con] 14 Mar 2013

Quasiparticle mass enhancement close to the quantum critical point in BaFe$_2$(As$_{1-x}$P$_x$)$_2$

P. Walmsley,[1] C. Putzke,[1] L. Malone,[1] I. Guillamón,[1] D. Vignolles,[2] C. Proust,[2] S. Badoux,[2] A.I. Coldea,[3] M.D. Watson,[3] S. Kasahara,[4] Y. Mizukami,[4] T. Shibauchi,[4] Y. Matsuda,[4] and A. Carrington[1]

[1] *H. H. Wills Physics Laboratory, University of Bristol, Tyndall Avenue, Bristol, BS8 1TL, United Kingdom.*
[2] *Laboratoire National des Champs Magnétiques Intenses (CNRS-INSA-UJF-UPS), 31400 Toulouse, France.*
[3] *Clarendon Laboratory, Department of Physics, University of Oxford, Oxford OX1 3PU, United Kingdom.*
[4] *Department of Physics, Kyoto University, Sakyo-ku, Kyoto 606-8502, Japan.*

We report a combined study of the specific heat and de Haas-van Alphen effect in the iron-pnictide superconductor BaFe$_2$(As$_{1-x}$P$_x$)$_2$. Our data when combined with results for the magnetic penetration depth give compelling evidence for the existence of a quantum critical point (QCP) close to $x = 0.30$ which affects the majority of the Fermi surface by enhancing the quasiparticle mass. The results show that the sharp peak in the inverse superfluid density seen in this system results from a strong increase in the quasiparticle mass at the QCP.

Recently there has been much interest in the idea that superconductivity in the iron-pnictides is boosted by the presence of a quantum critical point (QCP) located at the zero temperature end point of antiferromagnetic phase transition [1]. It has been suggested that the presence of quantum critical fluctuations close to this point increase the superconducting transition temperature by increasing the strength of the pairing interactions and / or by increasing the energy of the normal state relative to the superconducting state.

In most iron-pnictides experimental evidence for quantum critical fluctuations has been difficult to find as its effects are easily masked by inhomogeneity and impurity scattering. BaFe$_2$(As$_{1-x}$P$_x$)$_2$ provides a particularly clean system in which to study these effects as the substitution of As by the isovalent ion P suppresses antiferromagnetism and induces superconductivity [2] without changing the electron/hole balance and without inducing appreciable scattering [3, 4]. These are likely the main reasons why the effect of the QCP on the physical properties are so clearly visible experimentally in BaFe$_2$(As$_{1-x}$P$_x$)$_2$ but not in its charge doped counterparts. Experimental evidence for quantum critical fluctuations in this system near the critical point $x_c \simeq 0.3$ include a funnel of T-linear behavior in the resistivity centered on x_c [5] and an increase in effective mass on one of the electron Fermi surfaces, as measured by the de Haas-van Alphen (dHvA) effect [3], as x approaches x_c. Nuclear magnetic resonance (NMR) experiments show that the magnetic ordering temperature approaches zero at x_c [6]. Most recently, measurements of the magnetic penetration depth λ showed a large peak in λ at x_c indicating that the superfluid density is minimal at this critical x value and therefore that the QCP survives under the superconducting dome [7].

Although the above experiments have clearly shown that quantum critical fluctuations are present in this system close to x_c, so far it is less clear if the quasiparticle mass renormalization is the main factor which is causing the observed reduction in the superfluid density at x_c [8] or whether or not it is significant on all Fermi surface sheets. Here we report a combined study of the specific heat and dHvA effect of BaFe$_2$(As$_{1-x}$P$_x$)$_2$ which indicates a strong increase in the effective mass in good *quantitative* agreement with the superfluid density measurements as suggested by recent theoretical work [8].

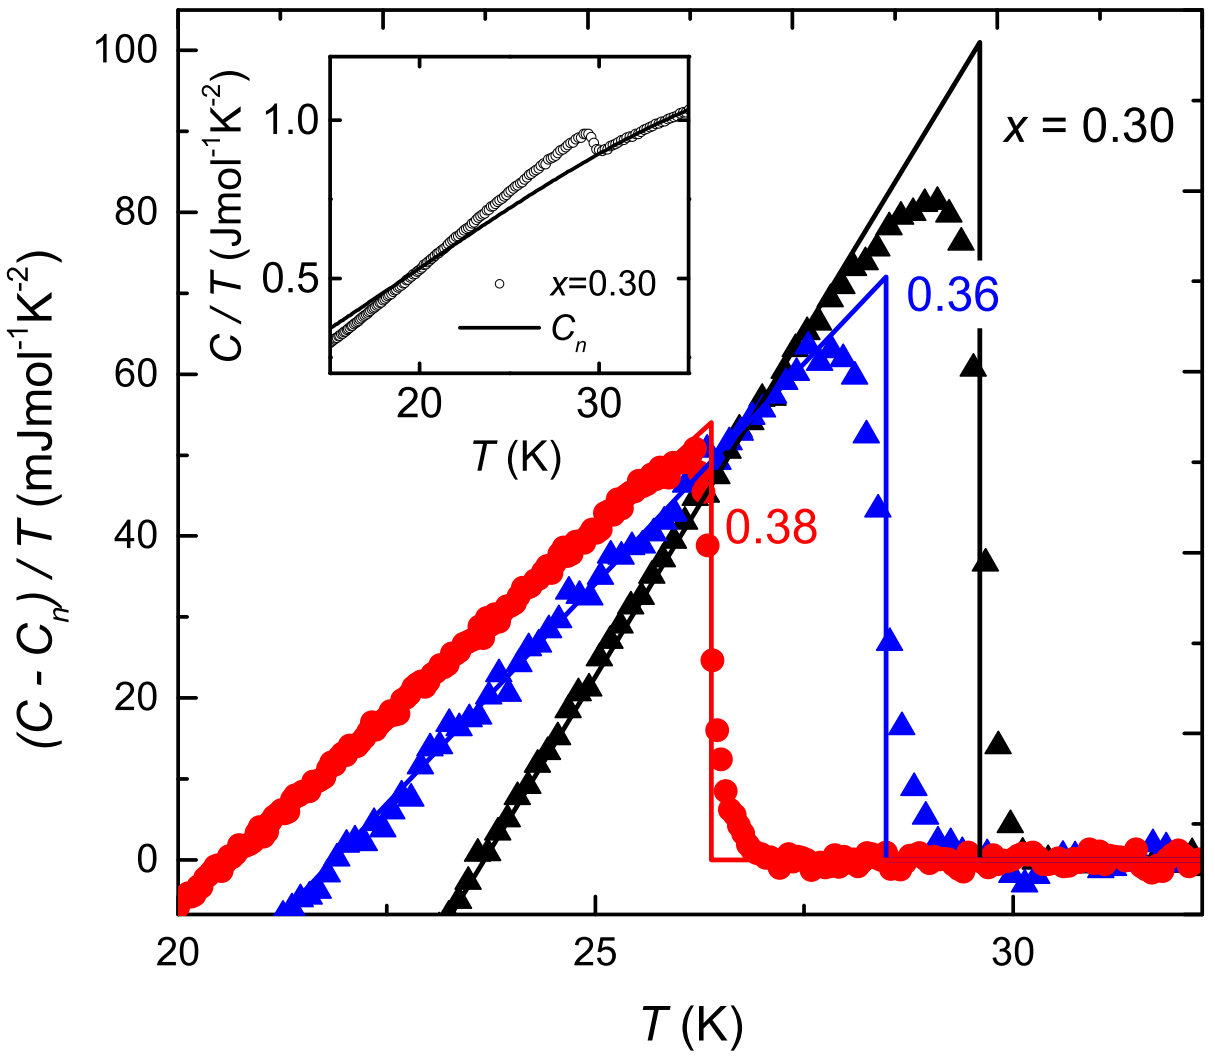

FIG. 1: (color online) The inset shows the total measured specific heat for a sample of BaFe$_2$(As$_{1-x}$P$_x$)$_2$ with $x = 0.30$, the solid line is the fitted normal state background C_n. The main part of the figure shows the specific heat with the normal state C_n subtracted for different values of x and the solid lines show the construction used to determine the jump height ΔC and T_c.

Single crystals of BaFe$_2$(As$_{1-x}$P$_x$)$_2$ were grown by a self-flux technique as described previously [5]. A particular requirement of both our specific heat and dHvA studies was to have very homogeneous samples. To this end we mostly focused on using small crystals with masses 4–70 μg for specific heat and 0.1–4 μg for dHvA. To measure the specific heat of such small samples we used a custom build microcalorimeter, where the thermometry elements and heater are deposited as thin films on a SiN membrane. Calibration of this device was checked by measuring high purity samples of Ag. We also used a more conventional long relaxation calorimeter [9] for some larger samples (of order 300 μg). In total around 30 samples were measured using the microcalorimeter and only those with the very sharpest superconducting transitions were retained for further analysis. For these samples, we made

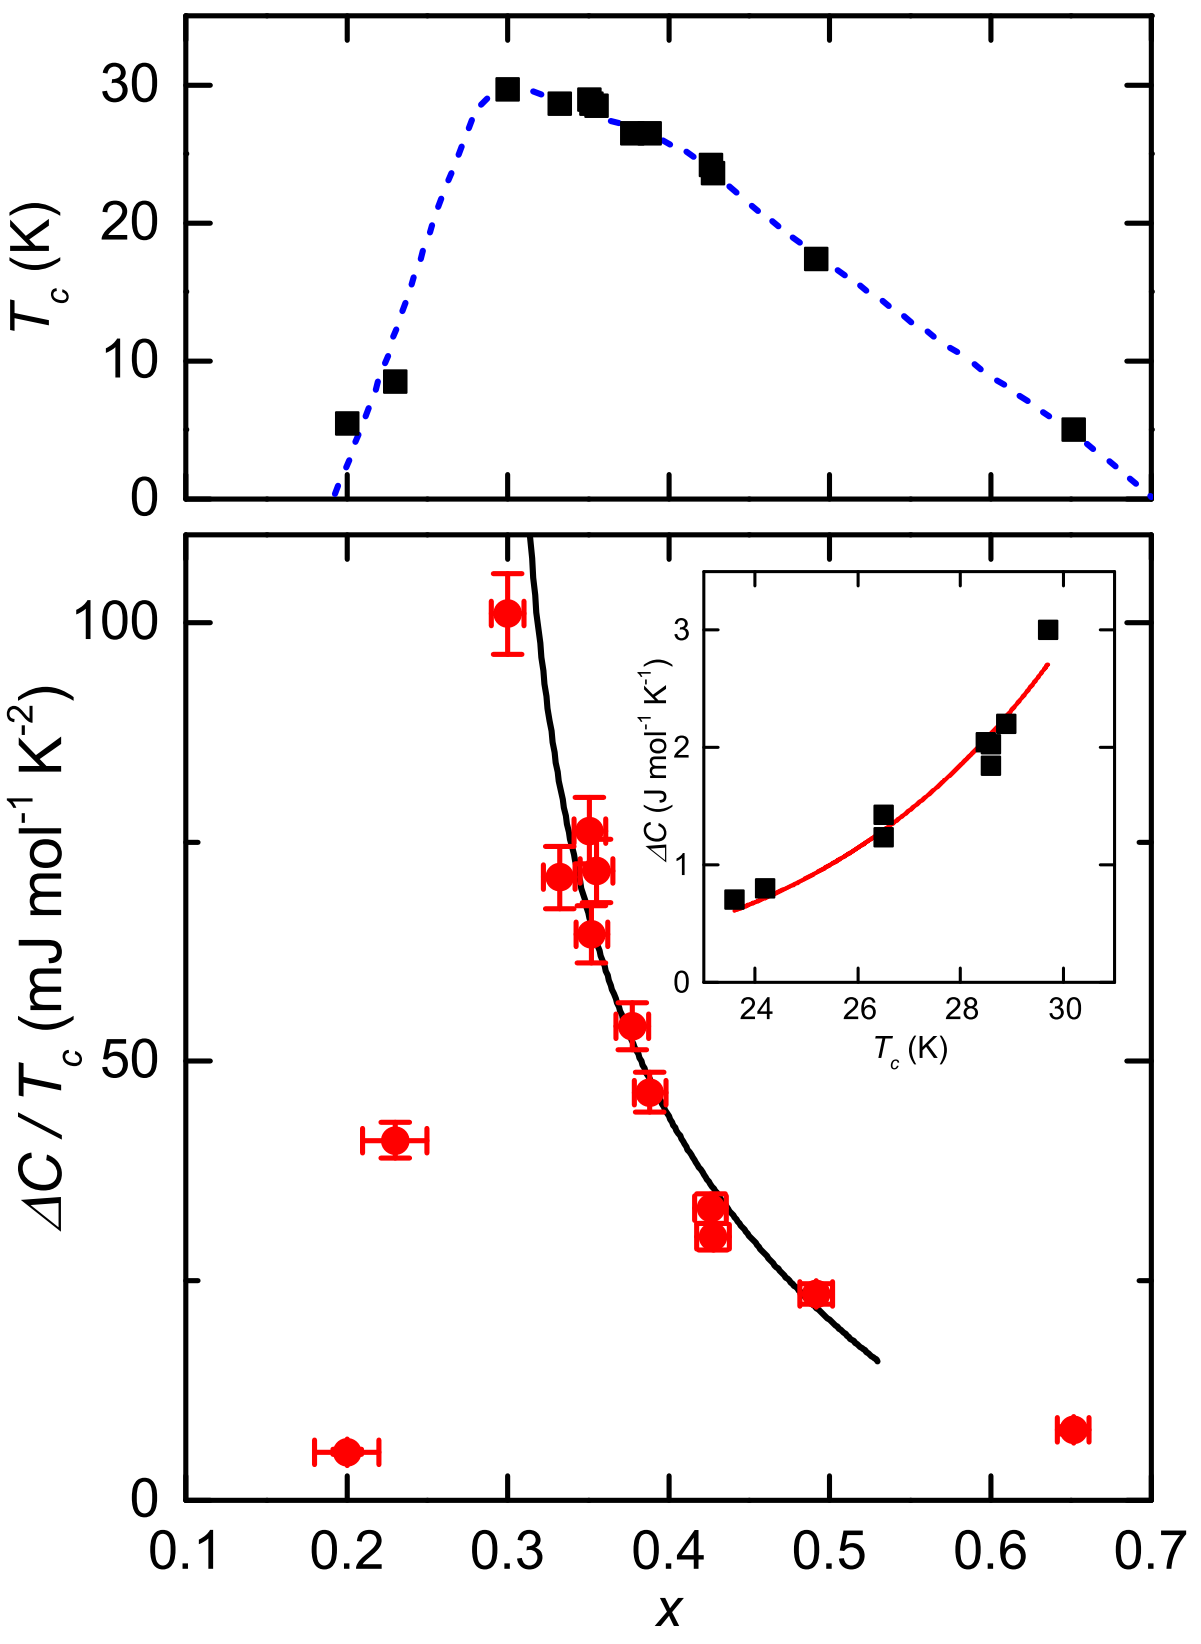

FIG. 2: (color online) The size of the jump in the specific heat $\Delta C/T_c$ as a function of x. The line shows a fit to the logarithmic behavior expected near a QCP. The inset shows ΔC vs T_c, with the solid line showing a fit to $\Delta C \propto T^n$. The x dependence of T_c is shown in the uppermost panel for the same samples and the dashed line is a guide to the eye.

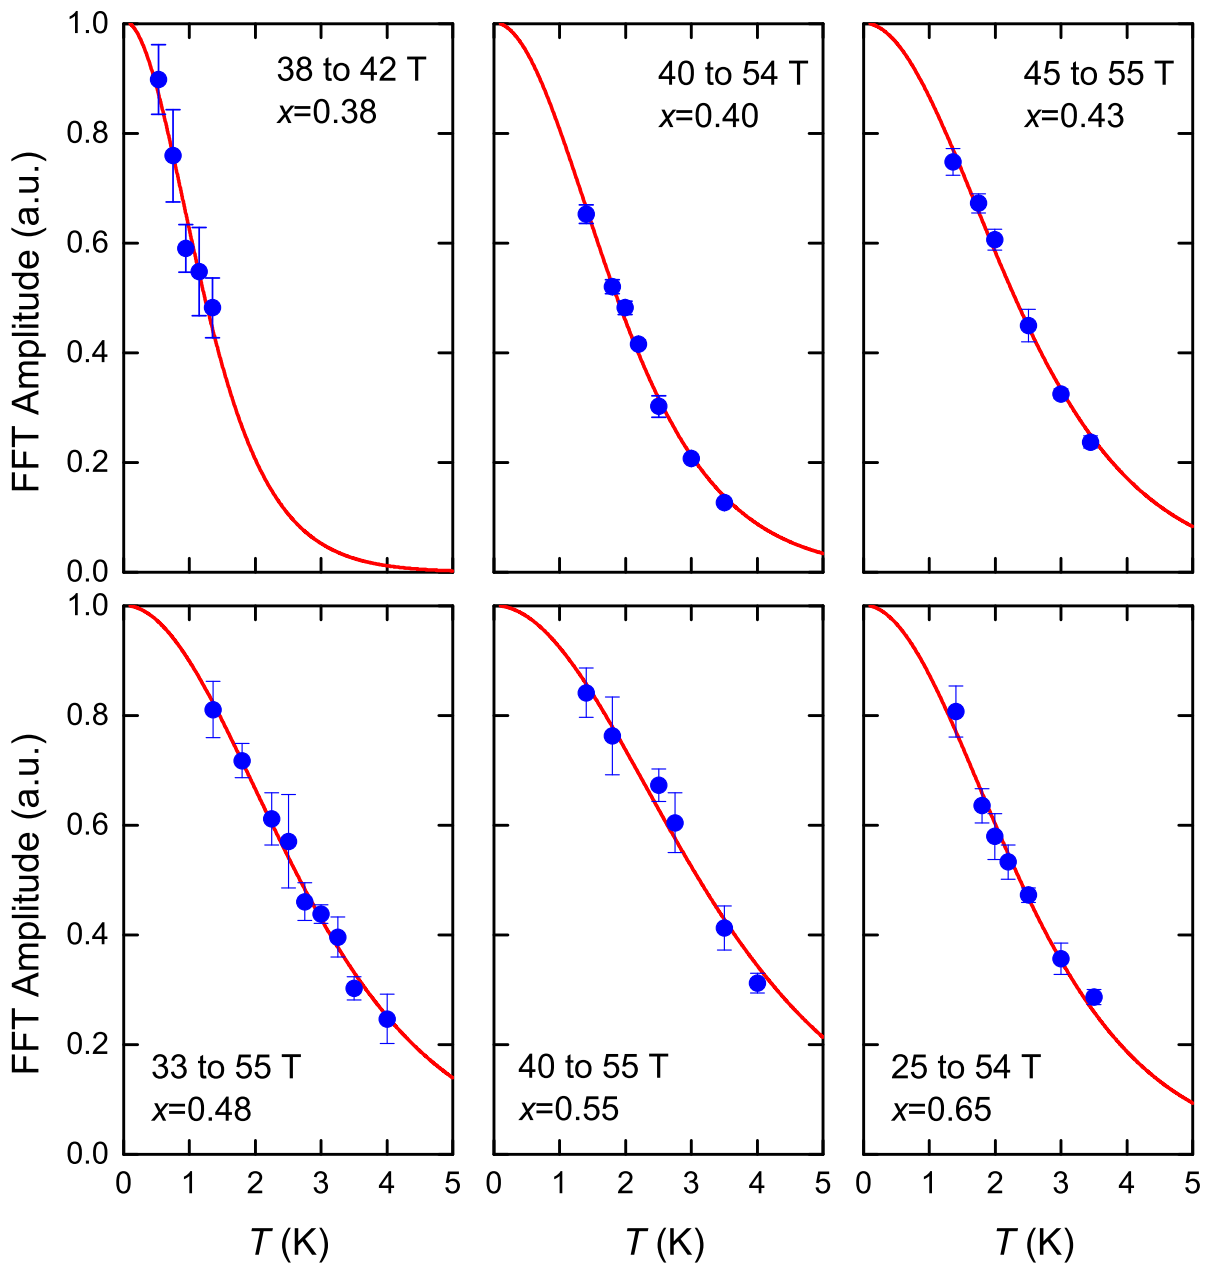

FIG. 3: (color online) Temperature dependent amplitude of fast Fourier transform (FFT) of the dHvA signal for the β orbits for samples with different value of x. The lines are fits to the LK formula. The field range and temperatures are indicated in the plots.

careful x-ray measurements to determine accurately the lattice constants and then used Vegard's law in conjunction with the lattice parameters for BaFe$_2$As$_2$ and BaFe$_2$P$_2$ to determine the value of x. dHvA measurements were performed by the torque method using micro piezoresistive cantilevers in both pulsed field (up to 60 T in Toulouse) and static field (up to 45 T in Tallahassee). Density functional theory (DFT) band-structure calculations were performed using Wien2K as described previously [10].

In Fig. 1 we show the jump in the specific heat C at T_c for samples with x close to x_c. Here the anomaly at the transition ΔC has been isolated from the phonon dominated background by subtracting a second order polynomial fitted above T_c and extrapolated to lower temperature. Although there would be some uncertainty in using this procedure over an extended temperature range, the lack of appreciable thermal superconducting fluctuations, as evidenced by the mean-field-like form of the anomaly, means that there is very little uncertainty in the size of ΔC.

It is evident from the data in Fig. 1 that the size of the anomaly $\Delta C/T_c$ depends very strongly on x and T_c. This is shown in more detail in Fig. 2. As the strong increase in ΔC with x is accompanied by a relatively small increase in T_c close to the critical point it seems highly unlikely that the coupling strength is the main factor. Indeed the normalized slope of $C(T) - C_n(T)$ just below T_c, $(T_c/\Delta C)d(C - C_n)/dT$, which depends strongly on the coupling strength [11], is almost independent of x for $0.3 < x < 0.5$ [12]. Instead we suggest that this increase in ΔC reflects the increase in the normal state density of states and hence the Sommerfeld coefficient γ. We show below that this interpretation gives remarkably good agreement with measurements of the quasiparticle mass from other techniques. We find that our data, for $0.5 \gtrsim x \gtrsim 0.3$, are well described by the logarithmic critical behavior, $\Delta C/T_c = c_0 + c_1 \ln(x - x_c)$, expected close to a QCP [1].

A strong increase in ΔC with T_c has been observed previously in many different iron based superconductors including BaFe$_2$(As$_{1-x}$P$_x$)$_2$ [13, 14]. Bud'ko, Ni and Canfield (BNC) [13] found that the data for materials with a wide range of T_c could be described by the scaling law $\Delta C \propto T_c^3$. This has been interpreted as either originating from quantum critically [15] or from strong impurity pair breaking[16]. In our samples we find significant departures from this scaling and close to the critical doping a much stronger dependence on T_c is observed; a fit to the power law $\Delta C \propto T_c^n$ gives $n = 6.5 \pm 0.7$ for 30 K> T_c >23 K (inset Fig. 2).

Although our absolute values of C (including phonons) are similar to those reported in Ref. [14], for samples with the highest T_c we find values of ΔC which are up to a factor of two larger. The values of ΔC are very similar for the low

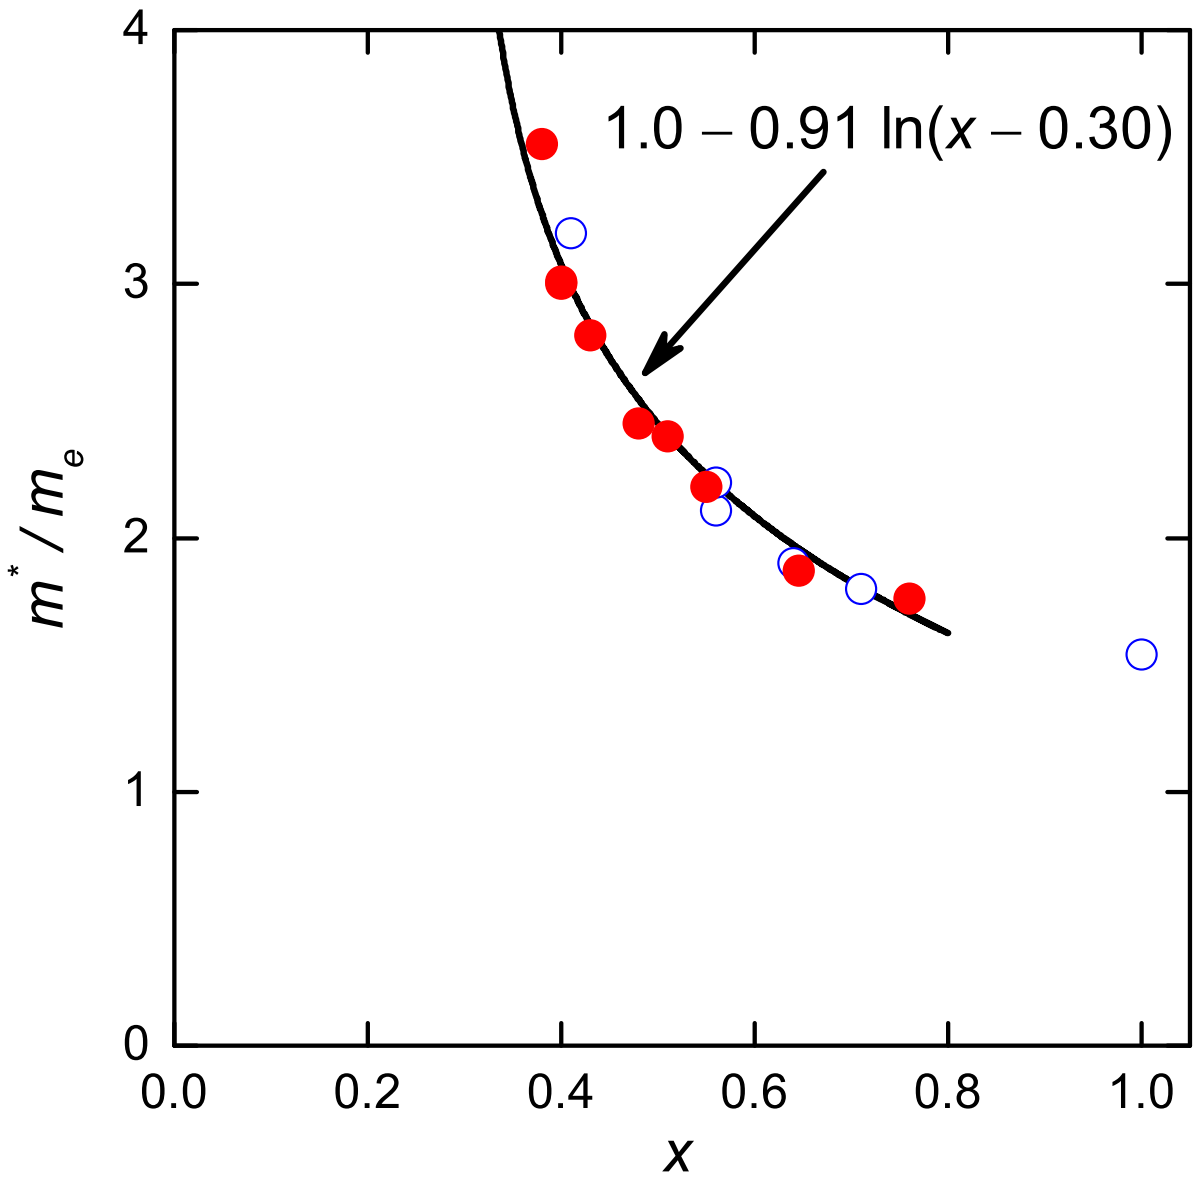

FIG. 4: (color online) Dependence of the measured dHvA mass of the β orbits on x, the solid symbols are the new data from the present study and the open symbols are from our previous studies [3, 10]. The solid line is a fit to the logarithmic behavior indicated.

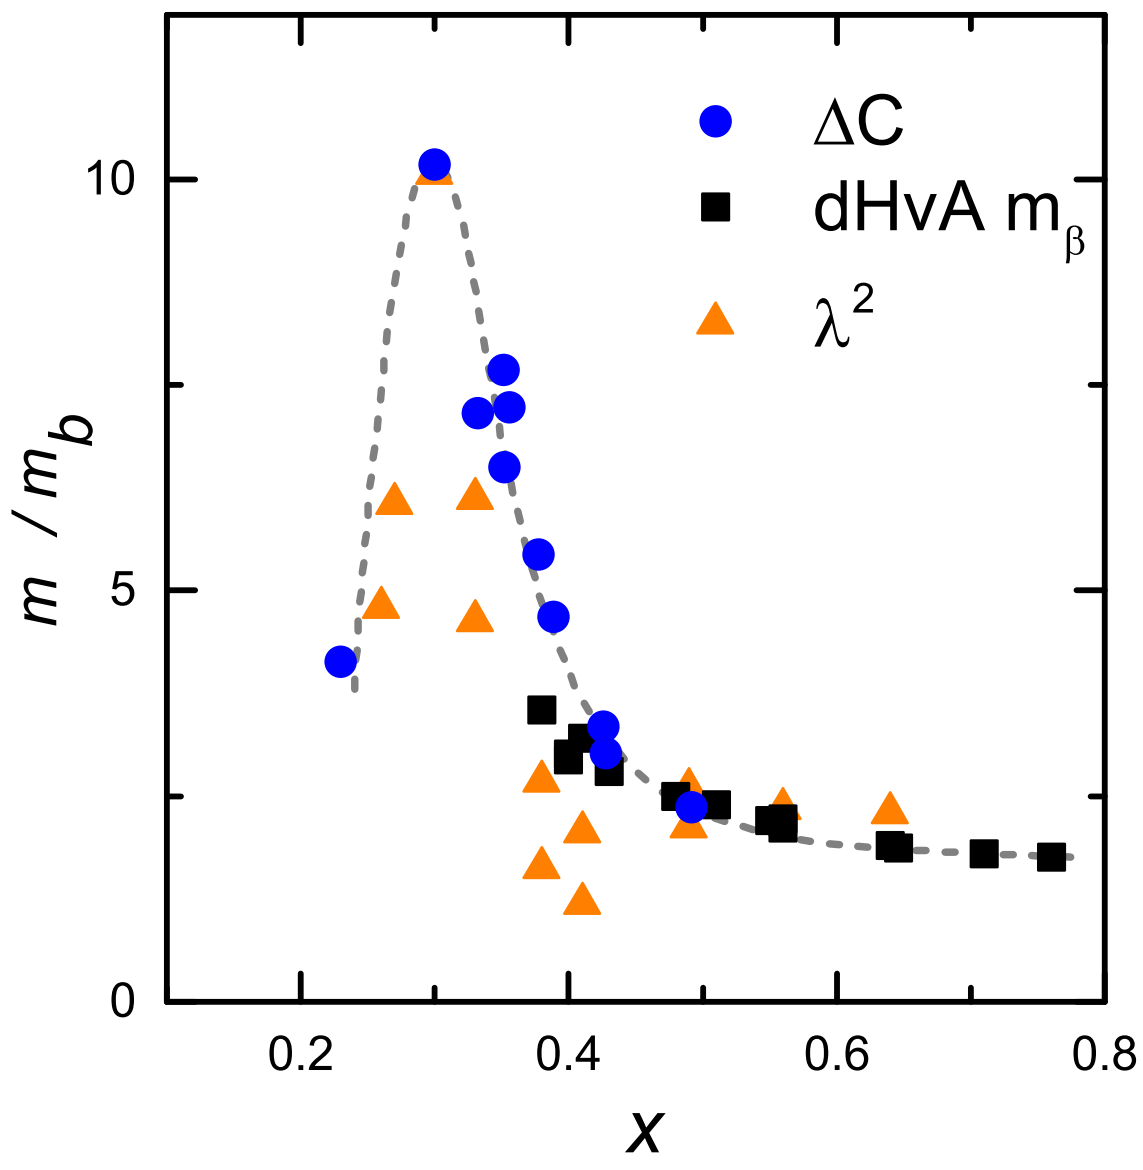

FIG. 5: (color online) Mass enhancements as derived from specific heat, dHvA and microwave magnetic penetration depth measurements[7]. The dashed line is a guide to the eye.

T_c samples. This difference likely arises from the higher homogeneity of the present samples. Indeed, we observed a similar reduction in ΔC for samples with broader transitions. The sharply peaked behavior of ΔC and strong asymmetry of $T_c(x)$ close to x_c (Fig. 2) naturally leads to a strong suppression of ΔC as the distribution of x within a sample becomes broader.

Specific heat measures the total density of the states (DOS) and so contains contributions from all the Fermi surface sheets. According to density functional theory calculations [10] for the end member $BaFe_2P_2$ the contributions from each sheet to the total DOS is 23% (band 1 hole), 37% (band 2 hole), 20% (band 3 electron), 20% (band 4 electron). So the contribution from the holes is a little higher than from the electrons but they are roughly equal. dHvA effect measurements have the potential to resolve quasiparticle masses from individual orbits on each Fermi surface sheet. For $BaFe_2P_2$ masses of almost all the observable orbits were reported by Arnold *et al.* [10]. All orbits had relatively uniform mass enhancements m^*/m_b ranging from 1.6 to 1.9. For the As substituted samples, the signals from the hole sheets are rapidly attenuated as x is decreased, but the signals from the inner (α) and outer (β) electron sheets less so [3]. The β orbits are the most prominent and can be tracked to the lowest value of x and hence highest T_c. In Fig. 3 we show how the amplitude of the dHvA signal from the β orbit reduces with temperature for several different values of x, along with fits to the standard Lifshitz-Kosevich (LK) formula [17] which is used to determine the orbitally averaged effective mass m^*_β.

In Fig. 4 we show the effective mass of these orbits over a wide range of doping, up to $x = 0.38$, $T_c = 28\,\mathrm{K}$ which is close to the maximum T_c. For the lower values of x we are not able to resolve the maximal and minimal β orbits separately because of the restricted range of inverse field over which the signal is observable, so this mass represents an average of the two. The small size of these samples makes the accurate determination of the lattice constants very difficult. It was shown previously [3] that the frequency of both the α and β electron orbits decreases linearly with x, so we used this fact to determine x. Because dHvA signals would be severely attenuated in any areas of the sample with inhomogeneous As/P content, this is a very accurate way to determine the exact x value for that part of the sample from which the dHvA signals originate. The solid line in Fig. 4 is a fit to the logarithmic form used for the specific heat. The point at $x = 1$ was not included in the fit as it is too far from the critical point.

We now make a quantitative comparison between the different measurements of effective mass. For the specific heat data, we first calculate γ from the measured values of $\Delta C/T_c$, using the relation $\alpha = \Delta C/\gamma T_c$. Although α does vary with the strength of the electron-boson coupling and the anisotropy of the superconducting gap, it only increases by a factor of $\sim$2 even for extremely strongly coupled superconductors like Pb [11]. Gap anisotropy decreases α, for example for d-wave α is 0.66 of the isotropic s-wave value. As both these effects are relatively small compared to the changes in $\Delta C(x)$ and will cancel each other out to some extent in $BaFe_2(As_{1-x}P_x)_2$ which has gap nodes [18], we make the approximation that α takes the weak coupling s-wave value of $\alpha = 1.43$ for all x. Then we calculate an average effective mass enhancement by taking the ratio of γ to the band-structure value calculated by DFT for $BaFe_2P_2$, $\gamma_b = 6.94\,\mathrm{mJ\,mol^{-1}K^{-2}}$.

For the penetration depth data we make a similar comparison to the DFT calculations. Using the experimental values of λ_0 at low temperature measured by the microwave cavity method [7], we estimate the renormalization from $m^*_\lambda/m_b = A\lambda_0^2/\lambda_b^2$. Here $A = n_{dHvA}/n_b = 0.358 + 0.44x$ is the measured shrinkage of the Fermi surface volume with x [3] divided by the DFT volume for $x = 1$ and $\lambda_b = 660\,\text{Å}$ is the DFT($x = 1$) value of λ. Although A is estimated from the electron sheet (α and β) dHvA data only, the hole sheets must shrink similarly because the material remains compensated for all x.

Finally, for the dHvA data we simply plot the measured values of m^*_β/m_b for the β orbits. We use the ($x = 1$) DFT m_b and γ_b values for all x for simplicity as these do not change appreciably with band energy shift corresponding to our range of x.

In Fig. 5 we compare these estimations of the different averages of the effective mass. The data are remarkably consistent within experimental error over most of the phase diagram. ΔC will be reduced at the edge of superconducting dome because of pair-breaking and sample inhomogeneity so we would not expect the samples with $x = 0.2$ and $x = 0.65$ to provide a good estimate of m^*. In principle, the mass enhancements could vary significantly between different Fermi surface sheets. In the quasi-classical theory the superfluid density $\lambda_x^{-2} \propto \int v_x^2|\boldsymbol{v}|^{-1}d\boldsymbol{S}$, and so the light electrons where the Fermi velocity $\boldsymbol{v}$ is high make the largest contribution. On the other hand, for the specific heat $\gamma \propto \int |\boldsymbol{v}|^{-1}d\boldsymbol{S}$ and so the heavy electrons contribute most. Hence the quantitative agreement between the trends for the mass enhancements indicated by λ^2, ΔC and the dHvA results for the electron β orbits tend to suggest that the mass enhancement is quite uniform over the Fermi surface. This does not exclude the presence of ‘hot spots’ or localized regions with much higher enhancement, which might result from regions that are particularly well connected by strong spin-fluctuation modes, but does suggest rather similar average enhancement for the electron and hole Fermi surfaces. This would be expected if the enhancement results from spin-fluctuated mediated scattering from the electron to hole surfaces with similar orbital character. These different experiments probe the quasiparticle mass in quite different regions of the (T, B) phase diagram. Penetration depth measures the mass at $T = 0, B = 0$, dHvA at $T = 0$ but high B, and specific heat ΔC at $B = 0$ and $T = T_c$. The numerical consistency between $\Delta C/T_c$ and λ^2 shown in Fig. 5 therefore also suggests that the finite T of order T_c does not significantly dampen the mass enhancements. The large B field used for the dHvA measurements also does not seem to have a strong effect except perhaps in the highest T_c sample measurable by dHvA ($x = 0.38$).

In summary, combined data for specific heat, de Haas-van Alphen effect and magnetic penetration depth [7] shows compelling evidence for the existence of a quantum critical point close to $x = 0.30$ in the BaFe$_2$(As$_{1-x}$P$_x$)$_2$ system, and that this effects the majority of the Fermi surface by enhancing the quasiparticle mass. The results show that the sharp peak in the inverse superfluid density seen in this system results from a strong enhancement of the quasiparticle mass at the QCP. The enhanced quasiparticle mass implies that the Fermi energy is suppressed, which is usually less advantageous for high T_c. The fact that the highest T_c is nevertheless attained right at $x_c = 0.3$ with the most enhanced mass strongly suggests that the quantum critical fluctuations help to enhance superconductivity in this system.

This work was supported by the EPSRC (UK), EuroMagNET II under the EU Contract No. 228043, and KAKENHI from JSPS. A portion of this work was performed at the National High Magnetic Field Laboratory, which is supported by National Science Foundation Cooperative Agreement No. DMR-0654118, the State of Florida, and the U.S. Department of Energy. I.G. acknowledges Marie Curie Intra-European Fellowship support under contract no. FP7-PEOPLE-2010-IEF-273105.

---

[1] E. Abrahams and Q. M. Si, J. Phys.-Condes. Matter **23**, 223201 (2011).

[2] S. Jiang, C. Wang, Z. Ren, Y. Luo, G. Cao, and Z. Xu, J. Phys. Cond. Mat. **21**, 382203 (2009).

[3] H. Shishido, A. F. Bangura, A. I. Coldea, S. Tonegawa, K. Hashimoto, S. Kasahara, P. M. C. Rourke, H. Ikeda, T. Terashima, R. Settai, Y. Onuki, D. Vignolles, C. Proust, B. Vignolle, A. McCollam, Y. Matsuda, T. Shibauchi, and A. Carrington, Phys. Rev. Lett. **104**, 057008 (2010).

[4] C. J. van der Beek, M. Konczykowski, S. Kasahara, T. Terashima, R. Okazaki, T. Shibauchi, and Y. Matsuda, Phys. Rev. Lett. **105**, 267002 (2010).

[5] S. Kasahara, T. Shibauchi, K. Hashimoto, K. Ikada, S. Tonegawa, R. Okazaki, H. Shishido, H. Ikeda, H. Takeya, K. Hirata, T. Terashima, and Y. Matsuda, Phys. Rev. B **81**, 184519 (2010).

[6] Y. Nakai, T. Iye, S. Kitagawa, K. Ishida, H. Ikeda, S. Kasahara, H. Shishido, T. Shibauchi, Y. Matsuda, and T. Terashima, Phys. Rev. Lett. **105**, 107003 (2010).

[7] K. Hashimoto, K. Cho, T. Shibauchi, S. Kasahara, Y. Mizukami, R. Katsumata, Y. Tsuruhara, T. Terashima, H. Ikeda, M. A. Tanatar, H. Kitano, N. Salovich, R. W. Giannetta, P. Walmsley, A. Carrington, R. Prozorov, and Y. Matsuda, Science **336**, 1554 (2012).

[8] A. Levchenko, M. Vavilov, M. Khodas, and A. Chubukov, arXiv:1212.5719.

[9] O. J. Taylor, A. Carrington, and J. A. Schlueter, Phys. Rev. Lett. **99**, 057001 (2007).

[10] B. J. Arnold, S. Kasahara, A. I. Coldea, T. Terashima, Y. Matsuda, T. Shibauchi, and A. Carrington, Phys. Rev. B **83**, 220504 (2011).

[11] J. P. Carbotte, Rev. Mod. Phys. **62**, 1027 (1990).

[12] Although $(T_c/\Delta C)d(C - C_n)/dT$ is quite sensitive to the background subtraction, particularly for samples with small ΔC anomalies.

[13] S. L. Bud’ko, N. Ni, and P. C. Canfield, Phys. Rev. B **79**, 220516 (2009).

[14] C. Chaparro, L. Fang, H. Claus, A. Rydh, G. W. Crabtree, V. Stanev, W. K. Kwok, and U. Welp, Phys. Rev. B **85**, 184525 (2012).

[15] J. Zaanen, Phys. Rev. B **80**, 212502 (2009).

[16] V. G. Kogan, Phys. Rev. B **81**, 184528 (2010).
[17] D. Schoenberg, *Magnetic Oscillations in Metals* (Cambridge University Press, Cambridge, England, 1984).
[18] K. Hashimoto, M. Yamashita, S. Kasahara, Y. Senshu, N. Nakata, S. Tonegawa, K. Ikada, A. Serafin, A. Carrington, T. Terashima, H. Ikeda, T. Shibauchi, and Y. Matsuda, Phys. Rev. B **81**, 220501 (2010).